

# Novel Electrical Joints Using Deformation Machining Technology—Part II: Experimental Verification

Lyudmila Solovyeva, Nikolay Zubkov, Bohdan Lisowsky, and Alaa Elmoursi

**Abstract**—This is the second part of the paper related to the exploration of deformation machining technology (DMT), originally developed at Bauman Moscow State Technical University, as it may apply to making electrical joints and comparing their performance to bolted and welded electrical joints. The DMT process is used to generate tooth-like profiles on two opposing surfaces that make the electrical joints which are later joined by applying a mechanical load. Part I contained a more detailed explanation of the DMT process and the description of the results of computer modeling of DMT joints in copper and aluminum. This paper provides the experimental results of the mechanical and electrical performance of copper and aluminum DMT joints which were compared to bolted and welded electrical joints of identical geometries. Measurements of tensile strength and electrical resistance, after thermal cycling and short-circuit testing, show equivalent or better performance of copper DMT joints compared with copper bolted and welded joints. In addition, it is observed that copper DMT joints have superior performance when compared with aluminum DMT joints, this was attributed to lesser gap filling and the springback effect that occurs after the mechanical load for making the joint is removed. The computer modeling results reported in Part I of this paper support these observations.

**Index Terms**—Deformation machining, edge joint, electrical resistance, lap joint, short circuit testing, springback, thermal cycling.

## I. INTRODUCTION

**E**LECTRICAL joints for high-current applications, exceeding 100 A, are typically made using bolting, welding, or brazing. This paper reports the mechanical and electrical performance data on joints made using a novel joining technology called deformation machining technology (DMT) [1]–[3]. DMT is based on using a specially designed cutting tool [1], [4], [5] that undercuts and lifts (mechanically deforms) the machined surface to form a tooth-like structure as shown in Fig. 1.

Manuscript received December 22, 2011; revised May 2, 2012; accepted May 7, 2012. Date of publication August 6, 2012; date of current version September 28, 2012. Recommended for publication by Associate Editor W. D. Brown upon evaluation of reviewers' comments.

L. Solovyeva and A. Elmoursi are with the Eaton Innovation Center, Eaton Corporation, Southfield, MI 48076 USA (e-mail: LyudmilaSolovyeva@eaton.com).

N. Zubkov is with Bauman Moscow State Technical University, Moscow 10505, Russia (e-mail: zoubkovu@bmstu.ru).

B. Lisowsky is with Materials Technology, Troy, MI 48085 USA (e-mail: Lisowsky@bohdan.cnc.net).

Color versions of one or more of the figures in this paper are available online at <http://ieeexplore.ieee.org>.

Digital Object Identifier 10.1109/TCPMT.2012.2199755

Computer modeling of copper and aluminum joints, as reported in Part I [6], showed that copper joints generate better joint contact manifested as a greater degree of gap filling, and better interlocking of the joined members than the aluminum joints as manifested by deformation angle and interference due to tooth upsetting. One of the difficulties identified in computer modeling of aluminum DMT joints is the springback after the joining force is removed, creating a gap between the adjacent DMT teeth. This paper compares the mechanical and electrical performance of DMT joints with that of bolted and welded joints. Successful implementation of copper DMT electrical joints for high-current carrying structures (exceeding 100 A) could possibly provide maintenance-free electrical enclosures by displacing bolted joints.

## II. OPTIMAL DMT PROFILE FOR COPPER AND ALUMINUM JOINTS

Based on the Part I computer modeling results [6], the optimal geometry elected for the evaluation of the mechanical and electrical performance was similar to M-Cu1 and M-Al2, with parameters as shown in Fig. 2 and Table I.

## III. EXPERIMENTAL SETUP AND RESULTS

Both lap and edge joints were subjected to a number of tests and evaluations and compared against standard bolted or welded joints.

Lap joint is defined as a joint between two plates, where the contact between the plates is made between the flat surfaces (width and length dimensions) of two plates. Edge joint is defined as a joint between two plates, where the contact between the plates is made on the short transverse surface (thickness and either width or length dimensions) of the two plates. Fig. 3 shows typical lap and edge joints.

### A. Thermal and Electrical Cycling—Lap Joint

Two standard bolted and one DMT joints, shown in Fig. 4, were subjected to thermal and power cycling at 100-A current in the following stated order.

Cycle 1) *Thermal Cycling*: 1 h at 100 °C/3 h at 30 °C; total cycles = 24.

Cycle 2) *Power Cycling*: 2 h ON/1 h OFF for 5 d.

Cycle 3) *Power Cycling at Variable Ambient*: 2 h current ON/1 h current OFF and 1 h at 50 °C/3 h at –5 °C for 2 d.

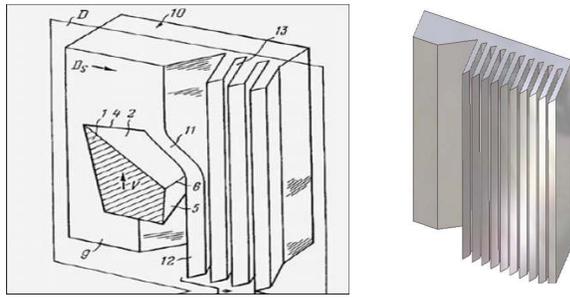


Fig. 1. Principle of DMT and a schematic of flat DMT surface.

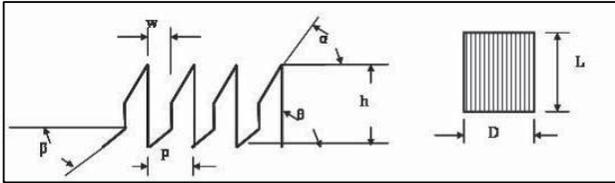


Fig. 2. Parameter nomenclature for DMT profile used in computer modeling.

TABLE I  
OPTIMAL TOOTH PROFILE AND ASSEMBLY LOADS FOR  
MACHINED COPPER AND ALUMINUM PLATES

DMT parameter	Dimension	Units	Variation	
			M-Cu1	M-Al2
Joint length	L	mm	20	20
Joint width	D	mm	20	20
Pitch	p	mm	1.28	1.28
Groove width	w	mm	0.73	0.73
Fin height	h	mm	1.83	1.83
Fin angle	$\theta$	degrees	90	90
Fin tip angle	$\alpha$	degrees	45	45
Root angle	$\beta$	degrees	45	45
(Fin width)	(Ref)	mm	0.55	0.55
Assembly load	–	M-tons	17	10
Slenderness ratio	h/fin width	–	3.33	3.33

TABLE II  
TENSILE RESULTS OF LAP JOINTS AFTER THERMAL CYCLING

Joint	Type	Assembly force (tons)	Pull force (kN)	Comment
Cu-Cu	Bolted	Not applicable	8.6	Standard joint
Cu-Cu	Machined	17 tons	9.8	Joint slippage
Cu-Cu	DMT	17 tons	10.86	Some joint slippage
Al-Al	Machined	10 tons	1.9	Joint sliding
Al-Al	DMT	10 tons	2.1	Joint slippage

Potential drop (measured in millivolts) was measured across each copper joint at a nominal 100-A current after each of the environmental cycles and resulting resistance was computed. All measurements were made at room temperature, while the samples may be “cold” or “hot” as a result of either thermal or electrical or both cycles. Fig. 5 shows the results with the overall conclusion that the copper DMT lap joints have a slightly better performance compared to bolted joints as indicated by the consistently lower joint resistance.

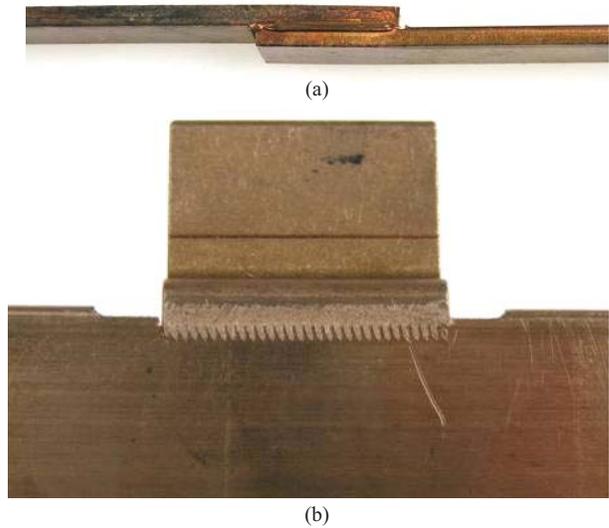


Fig. 3. Joints. (a) Lap joint. (b) Edge joint.

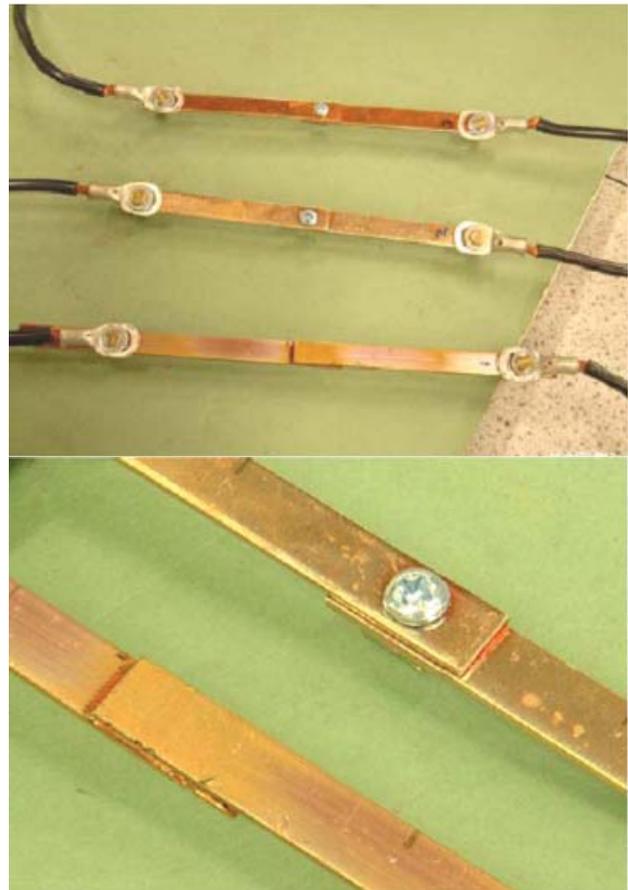


Fig. 4. Test samples of standard bolted joints and DMT joints used for testing.

*B. Short Circuit Test—Lap Joint*

Copper DMT and bolted lap joints were subjected to a short-circuit test of 12 kA for 0.1 s. Both bars bent under magnetic force and there was no separation or joint slippage in the DMT joint as seen in Fig. 6. In addition, the electric resistance of the DMT joint was unchanged after the SC test.

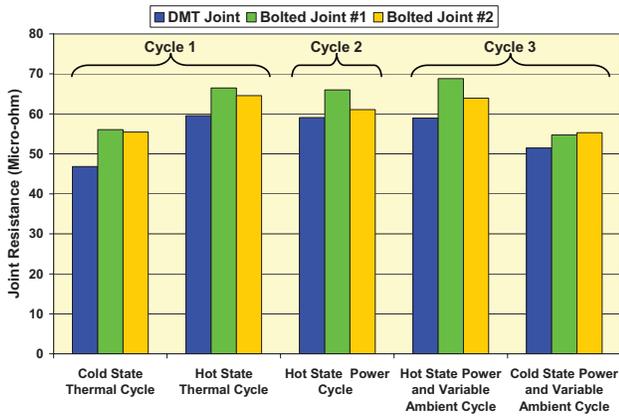


Fig. 5. Results of thermal and power cycling on copper joint electrical resistance.



Fig. 6. Lap and bolted lap joints after short-circuit test.

### C. Tensile Strength—Lap Joint

The lap joint, as shown at the right of Fig. 6, was tested in both the machined and DMT condition against standard bolted lap joint. The pull testing was done after the samples were subjected to thermal cycling, Cycle 1, above. Table II shows the results of the tensile tests.

These results show that the copper DMT joints have comparable tensile strength to bolted joints. Thermal cycling generates complex stresses seemingly loosening the aluminum machined DMT joint to the point of a very low strength. In light of that condition, DMT aluminum joints were not tested. Exclusion of aluminum joints from testing is also justified in the literature [7], [8].

### IV. POWERED TESTING OF EDGE JOINTS

Two sizes of edge joints were tested:

- 1) copper joint of 6-mm wide by 27-mm long at 400 A;
- 2) copper joint of 6.35-mm wide by 38.1-mm long at 200 and 300 A;
- 3) aluminum joint of 6.35-mm wide by 38.1-mm long at 200 and 300 A.

The 6-mm-wide by 27-mm-long joint was tested in “as manufactured” condition at 400 A, and the maximum temperature rise was recorded once the joint temperature stabilized to within  $\pm 0.1$  °C and the test data are shown in Table III.

TABLE III

TEST RESULTS ON 6-mm-WIDE BY 27-mm-LONG JOINTS AT 400 A

Joint type	Temperature rise (°C)	Maximum joint temperature (°C)
Copper DMT	17.0	39.6
Copper-standard welded	18.4	41.0

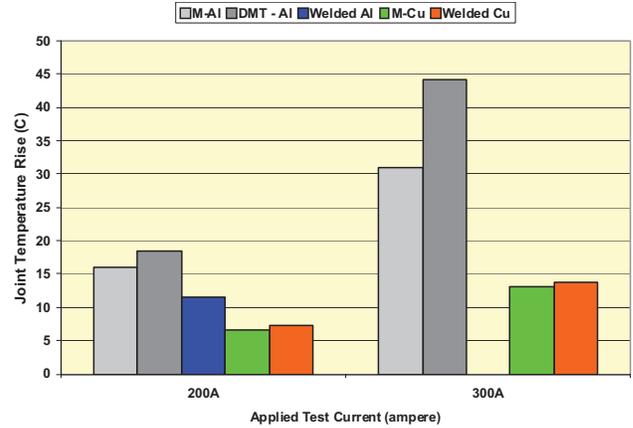


Fig. 7. Temperature rise for edge joints of 6.35 mm × 38.1 mm.

It is clear that the DMT joint is comparable if not better than the welded joint.

Edge samples of 6.35-mm wide by 38.1-mm long in copper and aluminum were tested at 200 and 300 A. The procedure for testing at 200 A required that the joint came to equilibrium for at least 1 h with a maximum temperature variation of  $\pm 1$  °C before the joint temperature rise was measured. After that test, the current was changed to 300 A, and under that condition, the aluminum DMT joint never thermally stabilized. The results are shown in Fig. 7. Clearly again, the Cu-machined and Cu-welded joints show similar performance. However, both the machined aluminum and the DMT aluminum joints showed higher temperature rise at the joint compared to the welded aluminum joint, at least at 200 A. At 300 A, both machined and DMT joints showed a significant rise in joint temperature which clearly indicates that these joints are not acceptable as a replacement to aluminum-welded joints.

### V. CONCLUSION

- 1) Copper DMT joints showed sufficient mechanical strength when compared to bolted joints and have an equivalent electrical performance to either bolted or welded joints.
- 2) Copper DMT joints appeared attractive for electrical joints provided that the DMT tooth characteristics could be accommodated by the joint design, particularly for edge joints.
- 3) As predicted during computer modeling, aluminum DMT joints showed inferior performance compared to copper DMT joints, which is believed to be due to the springback of the deformed teeth and the potential loosening during thermal cycling.
- 4) Aluminum DMT lap joints showed inferior performance compared to bolted and welded aluminum joints.

- 5) At 300-A power test of edge joint, the aluminum DMT joint never thermally stabilized, which was another indication of inferior performance when compared to copper DMT joints.
- 6) Tensile characteristics of DMT joints were directional and require appropriate design if that strength characteristic is required.

#### ACKNOWLEDGMENT

The authors would like to thank P. Hook and A. Jur, both from Eaton Electrical Sector, for performing the electrical tests on the lap joints and the edge joints, respectively. The authors would also like to thank R. Yanniello, also from Eaton Electrical Sector, for his insightful discussions and guidance throughout this technical paper.

#### REFERENCES

- [1] N. Zoubkov and A. Ovtchinnikov, "Method and apparatus of producing a surface with alternating ridges and depressions," U.S. Patent 5 775 187, Jul. 7, 1998.
- [2] R. Kukowski, "MDT-micro deformation technology," in *Proc. ASME Int. Mech. Eng. Congr. RD&D Expo*, Washington, DC, Nov. 2003, no. IMECE2003-42861, pp. 305–308.
- [3] *Technology of Deforming Cutting Mechanical Electrical and Thermal Connectors*. (2012) [Online]. Available: <http://www.defrez.ru>
- [4] P. Thors and N. Zoubkov, "Tool for making enhanced heat transfer surfaces," U.S. Patent 7 509 828, Mar. 31, 2009.
- [5] P. Thors, "Retractable finning tool and method of using," U.S. Patent 7 284 325, Oct. 23, 2007.
- [6] L. Solovyeva, B. Lisowsky, N. Zubkov, and A. Elmoursi, "Novel electrical joints using deformation machining technology—Part I: Computer modeling," to be published.
- [7] L. Pryor, R. Schlobohm, and B. Brownell, "A comparison of aluminum versus copper as used in electrical equipment," in *Proc. GE Ind. Newspaper*, Jan. 2011, pp. 1–7.
- [8] M. Braunovic, "Effect of connection design on the contact resistance of high power overlapping bolted joints," in *Proc. IEEE 47th Holm Conf. Elect. Contacts*, Sep. 2011, pp. 220–229.



**Lyudmila Solovyeva** received the Masters degree in material science and engineering from Aviation University, Russia, in 1978, and the Bachelors degree in physical metallurgy and heat treatment.

She was with the Materials Department, Kazan Aircraft Engine Building Production Association, as a Principal Engineer, and later, as a Materials Department Manager for almost 20 years. During this period, her major area of expertise was related to turbine blades. She was involved in research and development of special high-temperature and

corrosion-resistant diffusion multicomponent coatings for turbine blades, developing gamma-prime criteria in turbine blades to prevent creep, and developing a technology for reconditioning the microstructures of super alloy turbine blades. In the past 10 years, she was involved in the development of nickel single crystal for turbine blades. She was engaged in development of new materials for automotive components after the Kazan Engine Building Production Association formed a joint corporation with German bus transmission company "Voit." In 1997, she was with Akebono Engineering Brake System Company, Farmington Hills, MI, engaged in friction material characterization using scanning electron microscopy. In 1998, she joined the General Motors Engineering Center, Pontiac/Wixom, MI, where she was engaged in failure analysis of automotive parts for 3 years. In 2001, she joined the Eaton Corporation Southfield, MI as a Lead Engineer with the Materials, Fluids, and Chemicals Technology Group, Eaton Innovation

Center, where she was engaged in research and development of nanocoatings for DOE program, metal matrix composites for automotive components, advanced de-icing technology for automotive parts, and deformation machining technology from Russia. She has published more than ten research articles in journals and conferences and filed a U.S. patent application in 2009.



**Nikolay Zubkov** received the Degree from Bauman Moscow State Technical University (BMSTU), Moscow, Russia, in 1979, the Ph.D. degree in mechanical engineering in 1986, and the Doctor of Science degree in 2002.

He is currently the Laboratory Chief with the R&D Institute of Structural Materials and Technological Processes, BMSTU. He has specialized in machining and manufacturing engineering and is the developer of a new method of machining, deformational cutting. He proposed and justified new methods and

devices for obtaining new heat-transfer surfaces, including tube internal enhancement, restoring the original dimensions of worn machine parts by turning, making a capillary porous structures for heat pipes, and making fine filtering meshes from sheets, and slotted adjustable filter pipes quenching in lathe machining. He is the Head of the Tool Engineering and Technologies cycle of discipline. He has supervised implementation of more than 70 scientific researches. He has published 90 publications, including 25 inventions, five of which are protected by patents in Europe, the U.S., and other countries.

Dr. Zubkov was the recipient of the Gold Medal from the International Exhibition of Invention and Innovation six times, at Brussels, Geneva, Nuremberg, Seoul, Moscow, and Kuala-Lumpur. He was also the recipient of the Grand Prix and the Cup of Asia for Best Invention on ITEX, Malaysia, in 2010, and the Professor Academic Title in 2008.



**Bohdan Lisowsky** completed the initial formal technical training in casting technology in Poland. He received the Bachelors and Masters degrees in metallurgical engineering from Wayne State University, Detroit, MI, in 1964 and 1966, respectively.

He joined the Engineering and Research Center, Eaton Corporation, Southfield, MI, where he was involved in development of engine valve alloys for unleaded fuels, after a short work assignment with Argonne National Laboratory, Lemont, IL, where he was involved in developing a mercury amalgamation

process to detect oxygen content in liquid sodium for atomic reactors. During his 43 year career at Eaton, he conducted specialized materials testing and developed critical metallic and nonmetallic materials for engine valves, air bags, composite leaf springs, reaction-bonded silicon nitrides, and carbon-carbon friction materials. He has developed associated processes, specifications, and supply sources. He is the Chief Engineer and the Director of the Materials Engineering Groups in Southfield and Milwaukee in the developments of a variety of products, materials, and processes for all five of Eaton's market segments: aerospace, automotive, electrical, hydraulics, and truck. He has established an advanced coatings capability with the Innovation Center, Eaton, which led to obtaining a nanocoatings DOE contract. He secured or played a key role in three DOE contracts and was the Principal Investigator on a program to improve truck driveline efficiency working with Caterpillar, Peoria, IL, Northwestern University, Evanston, IL, and Argonne National Laboratory. He holds 17 U.S. patents and 42 foreign patents in Canada, Europe, Turkey, and Japan. In 2004, he was selected as one of five inaugural engineers of the year among engineers of Eaton for his work on carbon-carbon composite friction materials for truck transmissions. Currently, although retired in 2007, he has been a Consultant for Eaton's Innovation Center and the Vehicle Business Group.

Mr. Lisowsky was elected as a fellow of the ASM International and the Professional Materials and Metallurgical Society in 1993.



**Alaa Elmoursi** received the Ph.D. degree in electrical engineering from the University of Western Ontario, London, ON, Canada, in 1985.

He worked with the General Motors Research Laboratory, Warren, MI, for 14 years, where he was engaged in basic and applied research on electrostatic painting of liquids and powders, conductive plastic surfaces, plasma source ion implantation, DLC, and vacuum-based thin-film coating technologies. In 1991, he joined Delphi Research Laboratory, San Diego, CA, and was involved in research and development in thermal spray and cold spray coatings for numerous applications related to automotive components. At Delphi, he was the Chief Scientist for Delphi Thermal Division, a Group Leader for Coating Materials, and the Manager for Advanced Manufacturing and Material Processing. In 2007, he joined Eaton Corporation Southfield, MI as a Principal Engineer. He was the Principal Investigator for DOE program on nanocoatings and the Program Manager for Smart Materials. He is currently the Technology Manager with the Materials, Fluids and Chemicals Technology Group, Eaton Innovation Center. He has published over 50 research articles in referred journals and conferences and holds over ten U.S. and foreign patents. He has given many invited talks in his fields of expertise.